

Eastman chlorinated polyolefins

Formulating with Eastman waterborne CPO adhesion promoters

Useful as:

- Base resins for waterborne adhesion promoter primers
- Adhesion-promoting additives for waterborne coatings

The application of paint to polypropylene and TPO (thermoplastic polyolefin) is difficult because of the poor adhesion of most coatings to these plastics. Eastman CPO adhesion promoters are effective in improving paint adhesion to these substrates. With Eastman CPO dispersions, it is possible to apply an adhesion-promoting primer from a waterborne system or to promote adhesion of a waterborne coating through use as an additive.

Physical properties

Eastman CP 310W, CP 347W, and CP 349W are water dispersions of the same CPO resin. The major differences are the neutralizing amine in each dispersion and the presence of ethylene glycol in CP 347W and CP 349W. Physical properties are shown in Table 1.

Table 1. Typical properties^a

	Eastman CP 310W	Eastman CP 347W	Eastman CP 349W
Wt% solids	30	25	26
Wt% CPO	24	20	20
Solvent	—	2% ethylene glycol	5% ethylene glycol
pH @ 25°C	9–10	9–10	9–10
Amine	Ammonia	2-amino-2-methyl-1-propanol	2-amino-2-methyl-1-propanol
Stability			
Shelf, 1 yr	No change	No change	No change
50°C, 4 wk	Slight settle	No change	No change
Freeze-thaw	Good	Good	Good


^aEastman makes no representation that product in any particular shipment will conform exactly to the values listed.

Generally, the faster-evaporating ammonia in CP 310W makes it more useful in adhesion-promoting primers that are air dried prior to application of the topcoat. The 2-amino-2-methyl-1-propanol in CP 347W and CP 349W makes them more compatible with other waterborne resins and therefore more useful as additives. However, there are exceptions to these generalizations, depending on the other components of the substrate/coating system.

Use as primers

Eastman CPO dispersions are useful as base resins in adhesion-promoting primers. Primer performance with various topcoat systems is shown in Figure 1. This data shows that primer performance is generally comparable to that of solventborne CPOs.

Figure 1. Humidity resistance of CPO primers^{a,b}, % retained adhesion

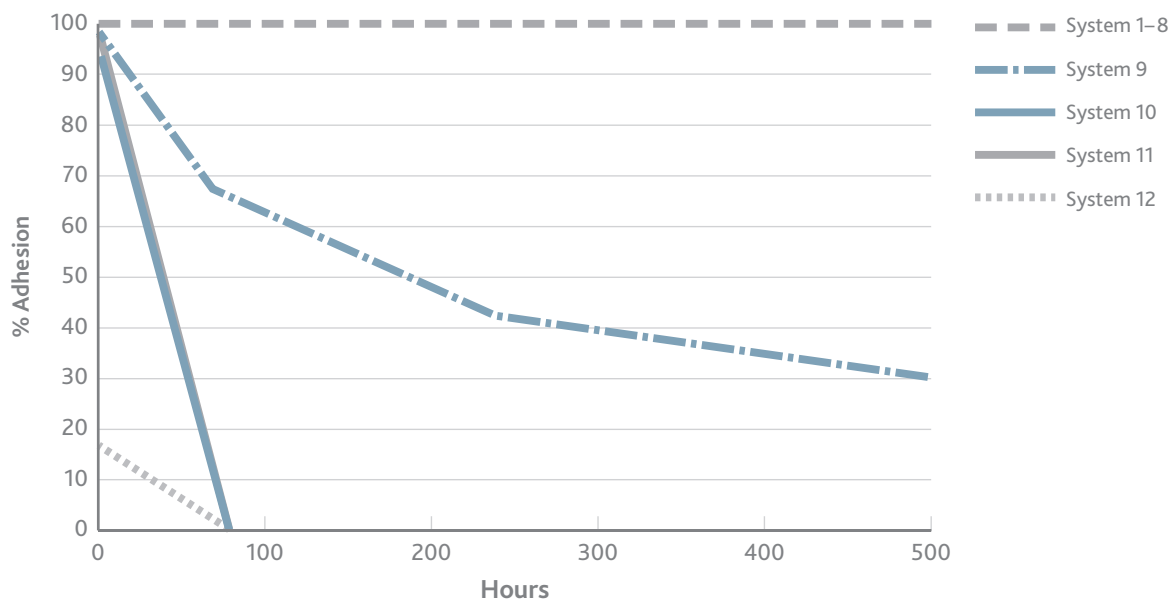

System		Primer ^d	Blisters ^e	Time, h
1	PEBC ^c	CP 343-1	—	—
2		CP 310W	10F	168
3		CP 347W	—	—
4		CP 349W	—	—
5	WBBC ^c	CP 343-1	10F	168
6		CP 310W	10F	168
7		CP 347W	—	—
8		CP 349W	10F	168
9	2KPUR ^c	CP 343-1	—	—
10		CP 310W	8M	71
11		CP 347W	10F	72
12		CP 349W	10F	71

^a50°C Cleveland humidity resistance (ASTM D4585). Substrate: Basell™ 3131 thermoplastic olefin.

^bCPO primer reduced to 5%–10% CPO, spray applied to give a 5–10 micron dry film thickness, and dried 6 h @ 25°C. Topcoats were spray applied and dried as directed. Data are mean % retained adhesion (ASTM D3359B) for 3 replicate panels after indicated duration in test.

^cPEBC = OEM metallic polyester base coat/clear coat, baked for 20 min @ 127°C. WBBC = OEM waterborne base coat/acrylic clear coat, baked for 20 min @ 127°C. 2KPUR = OEM 2K elastomeric polyester urethane, baked for 30 min @ 80°C.

^dCP 343-1 control applied as 5% solution in toluene. CPO dispersions reduced 1 part dispersion/2 parts water prior to application.

^eBlister size and density per ASTM D714. Time indicates point in test at which blisters appeared.

Primer formulations

To be an effective adhesion-promoting primer, the CPO film layer should be about 3–5 microns thick. CPOs are soft materials, and if the primer layer is too thick, it will tear apart, resulting in what appears to be an adhesion failure but is actually a cohesive failure. To achieve proper film thickness in a spray application, the CPO dispersion is usually reduced to 5–10 wt% solids prior to application.

Generally, CPO dispersion primers are formulated to help the waterborne system wet out the plastic and to reduce foam. Note that defoamers and additives that promote wet-out can sometimes reduce adhesion-promoting performance. This can be seen with the heavier alcohols in Table 2. Some glycol ether solvents can adversely affect adhesion, even though they appear to improve substrate wet-out.

Table 2. Effect of alcohols and defoamers on Eastman CP 310W, foaming tendency and adhesion performance

Alcohol/defoamer	Wt% ^a	Foaming	% Retained adhesion ^b	
			PP ^c	TPO ^d
None	—	Severe	100	100
Eastman <i>n</i> -propyl alcohol	20	Moderate	100	100
Eastman <i>n</i> -butyl alcohol	10	Slight	100	100
Eastman isobutyl alcohol	5	Moderate	100	100
	10	None	100	100
Eastman methyl amyl alcohol	5	None	60	200
	10	None	0	50
Eastman 2-ethylhexyl alcohol	5	Moderate	40	100
	10	Moderate— dispersion gelled	—	—
BYK-022 defoamer	0.1	Slight	100	100
BYK-023 defoamer	0.1	Slight	85	95
BYK-024 defoamer	0.4	Moderate	85	100
BYK-025 defoamer	0.6	Moderate	80	100
BYK-033 defoamer	0.6	Moderate	95	100
BYK-045 defoamer	0.3	Slight	90	90

^aBased on total weight of CP 310W

^bASTM D3359B

^cPolypropylene homopolymer P4G42-011

^d3131 thermoplastic polyolefin

Defoamer was added and CP 310W was shaken by hand.

CP 310W reduced 1 part CP 310W to 2 parts water, spray applied to give a 5-micron dry-film thickness, dried 6 h @ 25°C.

Topcoat is OEM metallic polyester base coat/acrylic clear coat baked 30 min @ 121°C.

Some higher-molecular-weight solvents can also adversely affect hot box stability if present at too high a concentration. It is suggested that any materials added to the CPO dispersion to aid wet-out or coalescence or to reduce foam be evaluated for their effect on adhesion-promoting performance and stability.

Tables 3 A, B, and C show suggested starting-point waterborne primer formulations for polypropylene substrates. These may be used to construct formulations to meet specific needs. The purpose of the polyurethane thickening agent in the formulation shown in Table 3 C is to allow the coating to “sit” on the substrate during solvent and water evaporation with minimal drawback. Other types of thickeners may also be used. The use of a thickener may allow for less use of solvents as wetting agents.

Thickening agents should be diluted and added with agitation for best formulation stability.

Table 3. Waterborne primer formulations for polypropylene substrates

A

Substrate	Wt%
Eastman CP dispersion ^a	29.0
Isobutyl alcohol	5.0
Eastman Texanol™ ester alcohol	1.0
Water	65.0
	100.0

^aCP 310W, CP 347W, or CP 349W

B

Substrate	Wt%	Wt%
Eastman CP dispersion ^a	29.0	29.0
Eastman EEH solvent	2.0	—
Eastman Texanol™ ester alcohol	—	3.0
Water	69.0	68.0
	100.0	100.0

^aCP 310W, CP 347W, or CP 349W. When using CP 310W, these formulations may have poor stability after long storage (>200 h @ 50°C).

C

Substrate	Wt%
Eastman CP dispersion ^a	29.1
DSX® 1514 polyurethane thickener	0.90
BYK-022	0.01
Deionized water	69.99
	100.0

^aCP 310W, CP 347W, or CP 349W

Note: Dilute the DSX 1514 in some or all of the water and add it under agitation.

Use as additives

Eastman CPO dispersions can be added directly to waterborne coating formulations to improve adhesion to polypropylene-based substrates. Generally, all three dispersions are compatible with most preneutralized dispersion resins. CP 347W and CP 349W are also compatible with many amine-neutralizable solution resins.

All three CPO dispersions improve adhesion of many acrylic dispersion resins. Of the three, CP 349W provides the best performance with polyurethane dispersion resins. CP 310W is generally not useful as an additive to polyurethane dispersion resins. The amount of CPO dispersion needed to improve adhesion depends on the substrate and other coating components.

The data in Table 4 illustrate compatibility of Eastman CPO dispersions in combination with a variety of coatings resins. Adhesion improvement is also shown.

Table 4. Resin compatibility and retained adhesion^a

Resin ^b	Type	Compatibility			0% CPO	% Retained adhesion on PP			0% CPO	% Retained adhesion on TPO		
		CP 10W	CP 347W	CP 349W		10% CP 310W	10% CP 347W	10% CP 349W		10% CP 310W	10% CP 347W	10% CP 349W
Dispersion resins												
NeoCryl™ XA-5090	Acrylic	C	C	C	0	80	100	100	0	100	100	100
NeoCryl A-6015	Acrylic	C	C	C	0	100	0	0	0	0	0	0
NeoCryl A-612	Acrylic	C	C	C	0	100	0	100	0	100	100	100
NeoCryl A-623	Acrylic	C	C	C	0	50	100	100	0	100	100	100
Joncryl™ 530	Acrylic	C	C	C	0	0	0	0	0	100	0	0
Joncryl 537	Acrylic	C	C	C	0	10	0	0	0	0	0	0
Rhoplex™ CL-104	Acrylic	C	C	C	0	100	50	100	0	40	100	50
Rhoplex WL-92	Acrylic	C	C	C	0	0	40	100	0	100	100	100
Rhoplex CL-103	Acrylic	C	C	C	0	100	0	100	0	100	100	70
NeoRez™ R-960 resin	Urethane	C	C	C	0	0	0	0	0	0	0	0
NeoPac™ R-9000	Urethane	C	C	C	0	0	10	100	0	80	100	100
Urotuf® L50	Urethane	C	C	C	0	0	0	100	0	0	100	100
Witcobond® W236	Urethane	C	C	C	0	0	20	100	0	0	100	100
Witcobond W404	Urethane	C	C	C	0	0	10	100	0	0	100	100
Solution resins^c												
Chempol® 310-1744	Acrylic	INC	C	C	0	—	100	100	0	—	100	100
Paraloid™ WR-97	Acrylic	INC	C	C	0	—	100	100	0	—	100	100

Legend

C = Compatible INC = Incompatible PP = P4G42-011 polypropylene homopolymer TPO = Himont™ 3131 thermoplastic olefin

^aCPO dispersions were added to resins to give 10% CPO based on resin solids.

^bSuppliers listed on page 6.

^cResins were neutralized with amine in CPO dispersion: ammonium hydroxide for CP 310W; AMP-95 for CP 347W and CP 349W.

Nonpolypropylene applications

Eastman CPO dispersions may be useful in promoting adhesion of waterborne coatings to plastics other than polypropylene. An example of this is illustrated in Table 5, which shows that CPO dispersion primers improve adhesion of a waterborne automotive OEM base coat to polyphenylene oxide (PPO).

Table 5. Adhesion of waterborne base coat over CPO primer on polyphenylene oxide

Substrate	Primer	% Retained adhesion
Noryl™ PX0844-780 polyphenylene oxide	None	0
	CP 310W	100
	CP347W	95

Raw material suppliers

Product	Supplier
Chempol® 310-1744	Arkema
DSX® 1514 polyurethane thickener	BASF
Henkel polyurethane thickener	Henkel Corporation
Joncryl™ 530 resin	BASF
Joncryl 537 resin	BASF
NeoCryl™ A-612 resin	DSM
NeoCryl A-623 resin	DSM
NeoCryl A-6015 resin	DSM
NeoCryl XA-5090 resin	DSM
NeoPac™ R-9000 resin	DSM
NeoRez™ R-960 resin	DSM
Noryl™ PX0844-780 polyphenylene oxide	GW Technologies, Inc.
Paraloid™ WR-97 resin	Dow Chemical
Rhoplex™ CL-103 resin	Dow Chemical
Rhoplex CL-104 resin	Dow Chemical
Rhoplex WL-92 resin	Dow Chemical
Urotuf® L50 resin	Reichhold
Witcobond® W236 resin	Lanxess
Witcobond W404 resin	Lanxess

Storage and handling of waterborne CPOs

Water-reducible adhesion-promoting dispersions generally exhibit good stability properties. Studies have shown that samples of each dispersion showed no performance change after five freeze-thaw cycles. **If freezing occurs, thaw and mix before using.**



Eastman Corporate Headquarters
P.O. Box 431
Kingsport, TN 37662-5280 U.S.A.

U.S.A. and Canada, 800-EASTMAN (800-327-8626)
Other Locations, +(1) 423-229-2000

www.eastman.com/locations

Although the information and recommendations set forth herein are presented in good faith, Eastman Chemical Company ("Eastman") and its subsidiaries make no representations or warranties as to the completeness or accuracy thereof. You must make your own determination of its suitability and completeness for your own use, for the protection of the environment, and for the health and safety of your employees and purchasers of your products. Nothing contained herein is to be construed as a recommendation to use any product, process, equipment, or formulation in conflict with any patent, and we make no representations or warranties, express or implied, that the use thereof will not infringe any patent. NO REPRESENTATIONS OR WARRANTIES, EITHER EXPRESS OR IMPLIED, OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE, OR OF ANY OTHER NATURE ARE MADE HEREUNDER WITH RESPECT TO INFORMATION OR THE PRODUCT TO WHICH INFORMATION REFERS AND NOTHING HEREIN WAIVES ANY OF THE SELLER'S CONDITIONS OF SALE.

Safety Data Sheets providing safety precautions that should be observed when handling and storing our products are available online or by request. You should obtain and review available material safety information before handling our products. If any materials mentioned are not our products, appropriate industrial hygiene and other safety precautions recommended by their manufacturers should be observed.

© 2019 Eastman. Eastman brands referenced herein are trademarks of Eastman or one of its subsidiaries or are being used under license. The ® symbol denotes registered trademark status in the U.S.; marks may also be registered internationally. Non-Eastman brands referenced herein are trademarks of their respective owners.