



High-solids polyester liquid coating resin formulations HS-3-5T and HS-3-6T

Based on Eastman TMPD™ glycol and Eastman™ purified isophthalic acid (PIA)

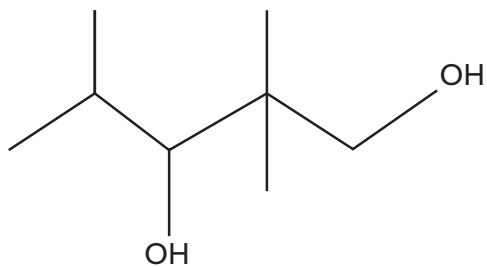

2,2,4-Trimethyl-1,3-pentanediol
CAS: 144-19-4



Purified isophthalic acid
CAS: 121-91-5

Features

HS-3-5T

- 2.72 lb/gal (326 g/L) determined VOC
- Excellent chemical and stain resistance
- Excellent corrosion resistance
- Good hardness

HS-3-6T

- 2.45 lb/gal (294 g/L) determined VOC
- Excellent chemical resistance
- Excellent corrosion resistance

The resin composition and processing procedure presented in this publication demonstrate the utility of Eastman TMPD™ glycol in a polyester resin for coating applications. These formulations have not been optimized for any particular property or end use. Alternative raw materials and process conditions should be considered to optimize for a particular application.

High-solids polyester liquid coating resin formulations HS-3-5T and HS-3-6T
Based on Eastman TMPD™ glycol and Eastman™ purified isophthalic acid (PIA) (Continued)

HS-3-5T resin formulation

Reactants	Equivalents	Moles	Wt, g
Eastman TMPD™ glycol	12.00	6.00	877
Trimethylolpropane (TMP)	1.65	0.55	74
Eastman™ purified isophthalic acid (PIA)	4.54	2.27	377
Adipic acid (AD)	4.54	2.27	332
		Charge	1,660
		H ₂ O	-160
		Yield	1,500

Catalyst: 3.3 g Fascat™ 4100 (0.2% based on total charge)

Processing procedure

- Charge all the reactants and catalyst to a 2-L reaction kettle equipped with a heating mantle, agitator, nitrogen purge, thermocouple, partial condenser, water trap, and total condenser. Reference Eastman publications N-345 and N-206 on glassware assembly and synthesis tips on Eastman TMPD™ glycol, respectively.
- Set the purge rate to 0.4 standard cubic feet per hour (SCFH) and increase the temperature to 200°C (392°F). Hold at 200°C for about 3 hours.
- Increase the temperature to a maximum of 210°C (410°F) and hold for a final acid number of 6 ± 2 (mg KOH/g resin) and a cone and plate viscosity of 0.35 to 0.50 Pa·s (3.5 to 5.0 P) at 100°C (212°F) or a Gardner-Holdt™ viscosity of Z–Z₂ at 85 wt % theoretical nonvolatiles in xylene.
- Allow the resin to cool to 140°C (284°F) and add 265 g xylene.

HS-3-6T resin formulation

Reactants	Equivalents	Moles	Wt, g
Stage 1			
Eastman TMPD™ glycol	12.24	6.12	895
Trimethylolpropane (TMP)	0.88	0.29	39
Eastman™ purified isophthalic acid (PIA)	4.38	2.19	364
Adipic acid (AD)	4.38	2.19	320
Stage 2			
Trimethylolpropane	0.88	0.29	39
		Charge	1,657
		H ₂ O	-157
		Yield	1,500

Catalyst: 1.6 g Fascat™ 4100 (0.1% based on total charge)

Processing procedure

- Charge all of the Stage 1 reactants and all of the catalyst to a 2-L reaction kettle equipped with a heating mantle, agitator, nitrogen purge, thermocouple, partial condenser, water trap, and total condenser. Reference Eastman publications N-345 and N-206 on glassware assembly and Eastman TMPD™ glycol synthesis tips, respectively.
- Set the purge rate at 0.4 standard cubic feet per hour (SCFH) and increase the temperature to 200°C (392°F). Hold at 200°C until approximately 78 mL (half of theoretical total) of distillate has been collected.
- Add the Stage 2 TMP and increase the reaction temperature to a maximum of 215°C (419°F). Hold at 215°C for a final acid number of 6 ± 2 (mg KOH/g resin) and a cone and plate viscosity of 0.05–0.20 Pa·s (0.5–2.0 P) at 125°C (257°F). Total time from start of up-heat to completion is about 6 hours.
- Allow the resin to cool to 140°C (284°F) and add solvent.

High-solids polyester liquid coating resin formulations HS-3-5T and HS-3-6T
 Based on Eastman TMPD™ glycol and Eastman™ purified isophthalic acid (PIA) (Continued)

Resin properties

	Formula	
	HS-3-5T	HS-3-6T
Equivalents of OH/equivalents of COOH (R value)	1.5	1.6
Target acid number, mg KOH/g resin	4–8	4–8
Calculated hydroxyl number, mg KOH/g resin	170	198
Determined molecular weight (by gel permeation chromatography)	800–1,000	900–1,100
Dilution solvent	Xylene	Xylene
Calculated nonvolatiles, % solids	85	85
Gardner-Holdt™ viscosity	Z–Z ₂	Z
Gardner™ color	1	1
Density, g/L (lb/gal)	1,051 (8.74)	1,041 (8.69)

Polyester/melamine enamel composition

Ingredients	Formula	
	HS-3-5T	HS-3-6T
	Wt%	
Resin formula (85 wt% in xylene)	39.40	40.3
Hexamethoxymethylmelamine	14.35	14.7
Ti-Pure™ R-960 TiO ₂	31.93	32.5
<i>p</i> -Toluenesulfonic acid catalyst (40 wt% in <i>i</i> -propanol)	0.36	0.4
Fluorosurfactant (20 wt% in Eastman™ EEP)	0.48	0.5
Eastman™ MAK (methyl <i>n</i> -amyl ketone)	10.00	7.6
Eastman™ EEP	0.96	2.0
Eastman™ PM acetate	0.64	—
Xylene	0.09	—
Eastman™ <i>n</i> -butyl alcohol	1.79	2.0
Total	100.00	100.00

High-solids polyester liquid coating resin formulations HS-3-5T and HS-3-6T
Based on Eastman TMPD™ glycol and Eastman™ purified isophthalic acid (PIA) (Continued)

Enamel properties

	Formula	
	HS-3-5T	HS-3-6T
Pigment/binder ratio	40/60	40/60
Polyester/melamine ratio	70/30	70/30
Density, ^a g/L (lb/gal)	1,322 (11.03)	1,316 (10.98)
Calculated nonvolatiles, wt%	76.4	80.9
Determined nonvolatiles, ^b wt%	75.3	79.3
Determined VOC, ^c g/L (lb/gal)	326 (2.72)	294 (2.45)
#4 Ford Cup viscosity, s	37	43

^aDetermined using a Byk-Gardner™ standard wt/gal cup.

^bTest performed according to ASTM Test Method D2369-90.

^cCalculation performed according to ASTM Test Method D3960-90 (10.1).

Cured film^a properties

	Formula	
	HS-3-5T	HS-3-6T
Film thickness, mils (microns)	1.3–1.8 (33–46)	1.3–1.8 (33–46)
Gloss, 60°/20°	89/76	—
Pencil hardness, scratch	2H	2H
Impact resistance, N-m (in.·lb)		
Direct	11 (100)	13.6 (120)
Reverse	2 (20)	5.6 (50)
Solvent resistance, MEK double rubs	200+	200+
1/8 in. Conical mandrel flexibility, ^b % pass	92	90
Cleveland™ humidity, ^c 40 h at 60°C (140°F)		
% gloss retention, 60°/20°	100/99	—
20° gloss retention, %	—	93
Blistering	V.V. few #8	none
Stain resistance		
Iodine for 30 min	Slight effect	Severe effect
Mustard for 24 hr	No effect	Slight effect
Ink for 24 hr	No effect	—
Chemical resistance ^d		
50% NaOH solution, 1 h at room temperature	No effect	No effect
50% H ₂ SO ₄ solution, 1 h at room temperature	No effect	No effect
Salt spray ^e resistance after 500 h	No creepage	Pass, ≤ 1/16 in. creepage

^aCoating applied to 20 gauge, cold-rolled, Bonderite™ 37 pretreated steel test panels. Baked 20 minutes at 149°C (300°F).

^bTest performed according to ASTM Test Method D522-88 (A).

^cTest performed according to ASTM Test Method D4585-87.

^dTest performed according to ASTM Test Method D1308-87.

^eTest performed according to ASTM Test Method B117-90

High-solids polyester liquid coating resin formulations HS-3-5T and HS-3-6T
 Based on Eastman TMPD™ glycol and Eastman™ purified isophthalic acid (PIA) (Continued)

HS-3-6T Viscosity^a profile

Solvent	Theoretical % solids	Determined % solids ^b	Gardner-Holdt™ viscosity	Brookfield viscosity cP
Xylene	95	88.3	Z ₈	1,420
	90	83.5	Z ₅	
	85	79.3	Z	
	80	74.5	U	
	75	69.3	J	
	70	64.8	E	
Aromatic™ 100	95	87.3	Z ₈	—
	90	82.3	Z ₅	
	85	78.0	Z ₁	
	80	73.5	V	
	75	68.2	K	
	70	62.5	E	
Eastman™ EEP	95	91.0	Z ₈	1,660
	90	85.0	Z ₅	
	85	79.7	Z ₁	
	80	75.6	V	
	75	70.6	M	
	70	65.8	G	
Eastman™ MAK (methyl <i>n</i> -amyl ketone)	95	89.4	Z ₇	808
	90	84.2	Z ₄	
	85	79.8	X	
	80	74.7	S	
	75	69.9	H	
	70	65.7	C	
Eastman™ PM acetate	85	77.6	—	1,930

^aDetermined at 25°C (77°F).

^bAfter 60 minutes at 110°C (230°F); reference ASTM D2369-90.

High-solids polyester liquid coating resin formulations HS-3-5T and HS-3-6T
Based on Eastman TMPD™ glycol and Eastman™ purified isophthalic acid (PIA) (Continued)

Raw material suppliers

Aromatic™ 100	Exxon
Adipic acid	DuPont
Eastman™ <i>n</i> -butyl alcohol	Eastman
Eastman™ EEP	Eastman
Fascat™ 4100 catalyst	Arkema
Hexamethoxymethylmelamine	Cytec
Eastman™ MAK (methyl <i>n</i> -amyl ketone)	Eastman
Eastman™ purified isophthalic acid (PIA)	Eastman
Ti-Pure™ R-900 TiO ₂	DuPont
Eastman TMPD™ glycol	Eastman
<i>p</i> -Toluenesulfonic acid	Aldrich
Trimethylolpropane	Geo Specialties, Perstorp



**Eastman Chemical Company
Corporate Headquarters**

P.O. Box 431
Kingsport, TN 37662-5280 U.S.A.
Telephone:
U.S.A. and Canada, 800-EASTMAN (800-327-8626)
Other Locations, (1) 423-229-2000
Fax: (1) 423-229-1193

Eastman Chemical Latin America

9155 South Dadeland Blvd.
Suite 1116
Miami, FL 33156 U.S.A.
Telephone: (1) 305-671-2800
Fax: (1) 305-671-2805

Eastman Chemical B.V.

Fascinatio Boulevard 602-614
2909 VA Capelle aan den IJssel
The Netherlands
Telephone: (31) 10 2402 111
Fax: (31) 10 2402 100

**Eastman (Shanghai) Chemical
Commercial Company, Ltd. Jingan Branch**

1206, CITIC Square
No. 1168 Nanjing Road (W)
Shanghai 200041, P.R. China
Telephone: (86) 21 6120-8700
Fax: (86) 21 5213-5255

Eastman Chemical Japan Ltd.

MetLife Aoyama Building 5F
2-11-16 Minami Aoyama
Minato-ku, Tokyo 107-0062 Japan
Telephone: (81) 3-3475-9510
Fax: (81) 3-3475-9515

Eastman Chemical Asia Pacific Pte. Ltd.

#05-04 Winsland House
3 Killiney Road
Singapore 239519
Telephone: (65) 6831-3100
Fax: (65) 6732-4930

www.eastman.com

Material Safety Data Sheets providing safety precautions that should be observed when handling and storing Eastman products are available online or by request. You should obtain and review the available material safety information before handling any of these products. If any materials mentioned are not Eastman products, appropriate industrial hygiene and other safety precautions recommended by their manufacturers should be observed.

Neither Eastman Chemical Company nor its marketing affiliates shall be responsible for the use of this information or of any product, method, or apparatus mentioned, and you must make your own determination of its suitability and completeness for your own use, for the protection of the environment, and for the health and safety of your employees and purchasers of your products. NO WARRANTY IS MADE OF THE MERCHANTABILITY OR FITNESS OF ANY PRODUCT, AND NOTHING HEREIN WAIVES ANY OF THE SELLER'S CONDITIONS OF SALE.

Eastman and TMPD are trademarks of Eastman Chemical Company.

All other brands are property of their respective owners.

© Eastman Chemical Company, 2013.