

Evaluation of various Eastman™ solvents

for use in dichloromethane-free
paint strippers

Evaluation of various Eastman™ solvents

for use in dichloromethane-free paint strippers

Paint strippers have traditionally contained dichloromethane (also called methylene chloride or DCM) as the active ingredient in the preparation. The crucial properties that make this solvent ideal for paint-removing operations are its excellent solvating powers, high volatility, and low flammability. Although DCM has been used for many years, recent concerns about its impact on human health have led to new legislation being implemented to restrict its use within the European Union from 2011 (Commission Decision 455/2009/EC).

It has been observed that DCM-free products are generally less effective in their primary function of paint removal. Hence, much effort is underway by industry participants to find safe and equally effective alternatives to DCM to ensure compliance with the new legislation. In an ideal world, the perfect replacement solvent for DCM would be as follows:


- As effective as DCM for paint removal
- Non-flammable and non-toxic
- Derived from a sustainable source
- Biodegradable
- No lasting impact on the environment

Eastman offers the paint-stripper formulator a wide choice of options to formulate effective DCM-free paint strippers (see Table 1).

The focus of this technical review is to highlight the benefits of Eastman™ n-butyl propionate in today's paint-stripper formulations, especially in combination with commonly used "active" paint-stripping solvents such as dimethylsulphoxide (DMSO), 1,3-dioxolane and 1-ethyl-2-pyrrolidone (NEP). This technical article also details the latest assessment methodology, Risk Characterization Ratio (RCR), an important ratio used to determine health and safety criteria.

Summary

Eastman™ n-butyl propionate enhances the performance of paint-stripper formulations and shows very good synergistic effects in combination with typical "active" solvents such as DMSO or NEP. It also has a very good RCR value which is favorable to improved health and safety.

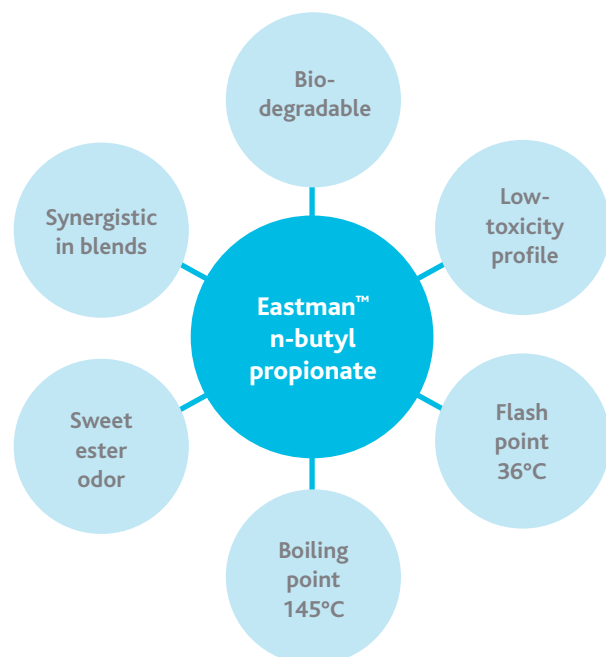

Wax helps to reduce the evaporation rate of volatile components of the paint-stripper formulation. Eastman™ EEP not only functions as an effective paint-stripper solvent but also is ideal for keeping the wax/hydrocarbon solvent blend in solution.

Table 1 Eastman's solvent range for paint strippers

	Bpt °C	Fpt °C	Properties
Eastman™ n-butyl propionate	145	36	Very good paint stripping on alkyd and acrylic multilayers. Synergistic action with DMSO and NEP.
Eastman™ EEP	165	59	Lower volatility. Very good paint stripping. Solubilizes wax in solution.
Eastman™ TEP	209	99	Lower volatility. Good paint stripping. Phosphate gives some flame retardancy.
Eastman™ EP	151	44	Good paint stripping with the ability to couple solvent and water-soluble components to form a compatible system.

Health and safety assessment

The solvents selected for assessment were based on analysis of commercially available paint strippers. To perform health and safety (HSE) assessments, Eastman turned to an independent industrial-hygiene consultant using state-of-the-art exposure calculation tools.¹ The RCR values have

been calculated for a given maximum single substance concentration (w/w %). RCR values <1.0 are generally considered to be safe. Table 2 lists the calculated RCR values and the general product-safety data.

Table 2 HSE assessments

Solvent	RCR outdoor brushing	RCR indoor brushing	Flammability class	Flash point (°C)	DSD classification 67/548/ EEC	CLP labeling EC 1272/2008	Biodegradability (OECD 310)
Eastman™ n-butyl propionate	0.11	0.72	R10	36 ^a	No	H226	Readily
Eastman™ EEP	0.00	0.03	None	59 ^a	No	H226; H066	Readily
Eastman™ EP	0.07	0.47	R10	44 ^a	R21; R36	H312; H319	Readily
Eastman™ TEP	0.12	0.79	None	99 ^b	Xn; R22	H302	Not readily
Butyl acetate	0.41	2.65	R10	27 ^c	R66; R67	H226; H336	Readily
Dibasic ester (di-methyl mixture)	0.01	0.02	None	100 ^c	No		Readily
Dibasic ester (di-methyl, methyl)	0.01	0.01	None	98 ^c	No		>60%

^aSetaflash closed cup

^bPensky-Martens closed cup

^cTag closed cup

¹Following REACH Guidance Document on Information Requirements and Chemical Safety Assessment recognized models such as ECETOC TRA, EASE, Consexpo, ART, Fugacity models, and SkinPerm have been applied to calculate the RCR. RCR is the ratio between calculated or measured exposure to a substance and the determined safe level of Derived No Effect Level (DNEL). Values below 1 are considered as safe, whereas values above 1 are considered unsafe. No difference between professional user and consumer has been taken as a position. Typical formulation concentration at 35% except for Eastman™ EP and Eastman™ EEP at 10%. Four-hour brushing with maximum 1 L of mixture. No risk-management measures have been assumed.

Synergistic paint-stripping comparisons

The paint-removal performance of Eastman™ n-butyl propionate was compared against DMSO and NEP paint-stripping solvents. The paint strippers were applied to a commercial multilayer alkyd or acrylic paint (3x 120µm WFT) and the stripping time in terms of softening and blistering was recorded. For alkyds, the time to blister down to the substrate was noted and for the acrylics, the time to soften down to the substrate was noted (Figures 1 and 2).

The evaluations show that there is a synergistic paint-stripping effect between DMSO and NEP with Eastman™ n-butyl propionate.

The paint-stripping efficiency of these solvents was significantly improved by mixing with Eastman™ n-butyl propionate.

Figure 1 DMSO and Eastman™ n-butyl propionate blends on multilayer alkyd and acrylic paint


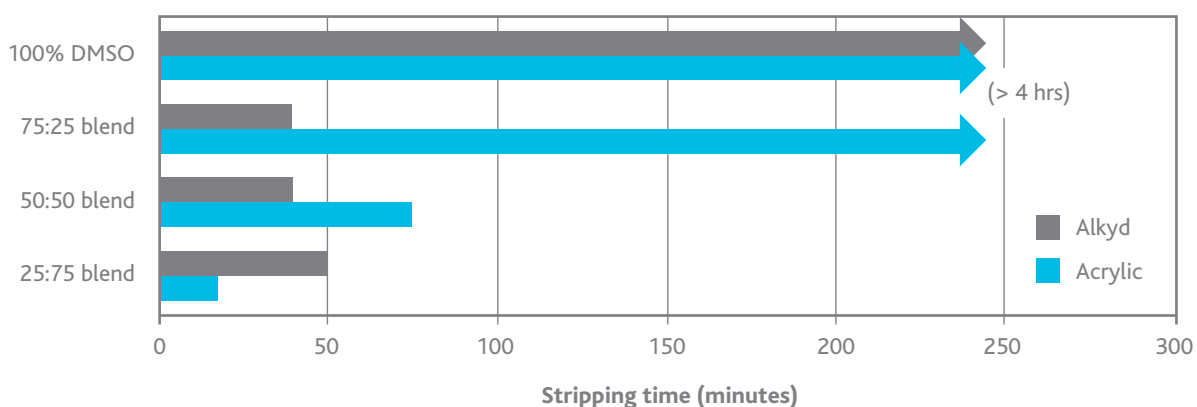


Figure 2 NEP and Eastman™ n-butyl propionate blends on multilayer acrylic paint

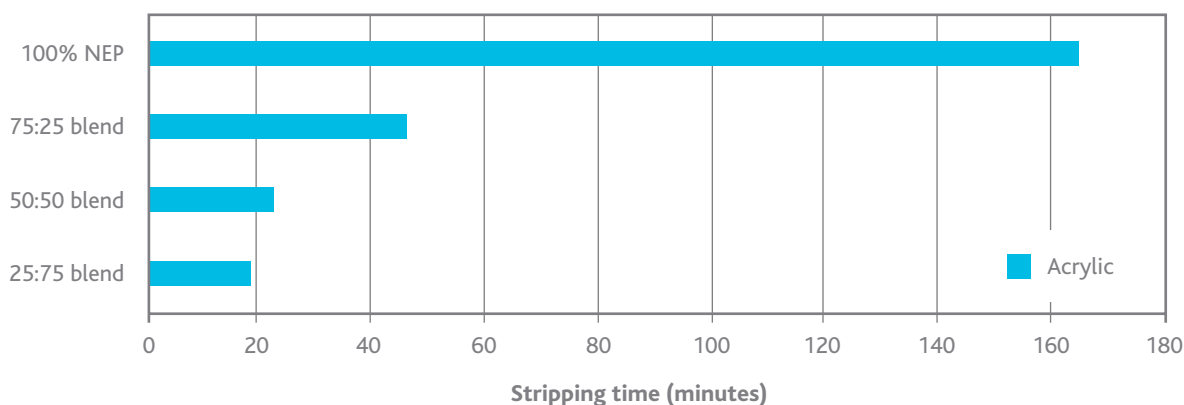

Performance evaluation of experimental paint strippers

A range of experimental products were formulated based on Eastman™ solvent(s) and compared to commercial products. To minimize solvent evaporation, a paraffin wax was incorporated into all three experimental removers. The use of Eastman™ EEP was found to help compatibilize the wax in solution and reduce phase separation. The benefits of the paraffin wax are as follows:

- Highly active solvent components remain in contact with the paint for longer.
- Less volatile solvent is emitted into the users' working environment.
- Wax additives can sometimes help a paint-remover composition achieve a lower flammability rating when tested for regulatory purposes.

To replicate "real-life conditions," the efficiency of the experimental and commercial paint strippers were evaluated on an old wooden door with an unknown number of paint layers. Evaluations were also carried out on a water-based acrylic, exterior facade plaster system (ref. Onip Grese RPE) that was applied by trowel at a thickness of 3.5 ± 0.5 mm to a standard gypsum board and fully dried for 8 weeks at 23°C.

The paint strippers were applied by brush application and a contact time of 60 minutes was allowed before physical stripping took place.

The starting-point formulations are shown in Table 3. The evaluations are in Figure 3 and show that the experimental systems with Eastman™ n-butyl propionate have a positive effect on paint-stripping efficiency that outperformed an average of seven commercial systems.

Table 3 Starting-point formulations

Experimental paint stripper 1 (Exp. PS 1)	
Ingredient	Weight
Dimethylsulphoxide (DMSO)	459.4
Ethanolamine	5.2
Methocel 311 ⁱ	14.4
Eastman™ n-butyl propionate	347.4
Eastman™ EEP Solvent	105.9
Empilan KTA 6 ⁱⁱ	5.2
Paraffin wax solution	62.5
9.375 parts Sasolwax 2477	
53.125 parts Exxsol D40	
Total	1000.0


Experimental paint stripper 2 (Exp. PS 2)	
Ingredient	Weight
1-Ethyl-2-pyrrolidone (NEP)	462.8
Ethanolamine	5.2
Methocel 311 ⁱ	13.2
Eastman™ n-butyl propionate	350.0
Eastman™ EEP Solvent	106.8
Empilan KTA 6 ⁱⁱ	4.8
Paraffin wax solution	57.2
9.375 parts Sasolwax 2477	
53.125 parts Exxsol D40	
Total	1000.0

Experimental paint stripper 3 (Exp. PS 3)	
Ingredient	Weight
1,3-Dioxolane	597.8
Methocel 311 ⁱ	12.2
Dimethoxymethane	99.6
Methyl ethyl ketone	109.5
Eastman™ n-butyl propionate	129.5
Paraffin wax solution	51.4
7.71 parts Sasolwax 2477	
43.69 parts Exxsol D40	
Total	1000.0

ⁱDow Chemical's cellulose ether thickener

ⁱⁱHuntsman's surfactant

Figure 3 Improved efficiency of experimental paint-stripper formulations containing Eastman™ n-butyl propionate

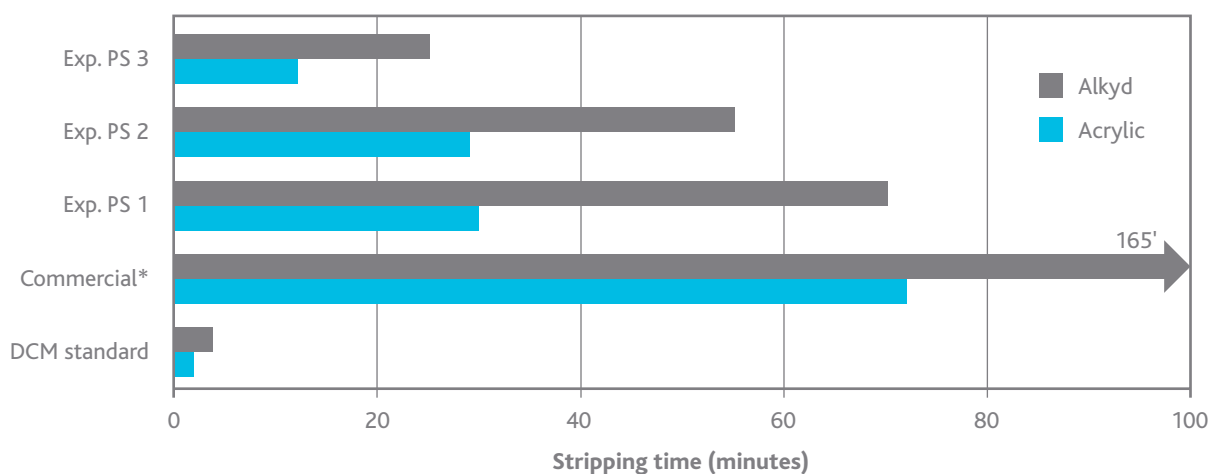

*Average of seven commercial products

Conclusion

Based on results of our experiments, we can conclude that Eastman™ n-butyl propionate can be used together with a wide range of solvents currently used in paint-stripper formulations.

- Eastman™ n-butyl propionate shows very good synergistic effects and reduces paint-stripping time significantly.
- Eastman™ n-butyl propionate has a very good RCR value which makes it a safe choice.
- Eastman™ EEP also works well as paint-stripper solvent. It was found to help compatibilize the wax in solution and reduce phase separation.
- Experimental formulations containing Eastman™ n-butyl propionate and EEP outperformed commercial paint strippers.

Eastman Chemical Company

Corporate Headquarters

P.O. Box 431
Kingsport, TN 37662-5280 U.S.A.

Telephone:
U.S.A. and Canada, 800-EASTMAN (800-327-8626)
Other Locations, (1) 423-229-2000
Fax: (1) 423-229-1193

Eastman Chemical Latin America

9155 South Dadeland Blvd.
Suite 1116
Miami, FL 33156 U.S.A.

Telephone: (1) 305-671-2800
Fax: (1) 305-671-2805

Eastman Chemical B.V.

Fascinatio Boulevard 602-614
2909 VA Capelle aan den IJssel
The Netherlands

Telephone: (31) 10 2402 111
Fax: (31) 10 2402 100

Eastman (Shanghai) Chemical Commercial Company, Ltd. Jingan Branch

1206, CITIC Square
No. 1168 Nanjing Road (W)
Shanghai 200041, P.R. China

Telephone: (86) 21 6120-8700
Fax: (86) 21 5213-5255

Eastman Chemical Japan Ltd.

AIG Aoyama Building 5F
2-11-16 Minami Aoyama
Minato-ku, Tokyo 107-0062 Japan

Telephone: (81) 3-3475-9510
Fax: (81) 3-3475-9515

Eastman Chemical Asia Pacific Pte. Ltd.

#05-04 Winsland House
3 Killiney Road
Singapore 239519

Telephone: (65) 6831-3100
Fax: (65) 6732-4930

www.eastman.com

EASTMAN

Material Safety Data Sheets providing safety precautions, that should be observed when handling and storing Eastman products, are available online or by request. You should obtain and review the available material safety information before handling any of these products. If any materials mentioned are not Eastman products, appropriate industrial hygiene and other safety precautions recommended by their manufacturers should be observed.

Neither Eastman Chemical Company nor its marketing affiliates shall be responsible for the use of this information, or of any product, method or apparatus mentioned, and you must make your own determination of its suitability and completeness for your own use, for the protection of the environment and for the health and safety of your employees and purchasers of your products. NO WARRANTY IS MADE OF THE MERCHANTABILITY OR FITNESS OF ANY PRODUCT, AND NOTHING HEREIN WAIVES ANY OF THE SELLER'S CONDITIONS OF SALE.

Eastman and The results of insight are trademarks of Eastman Chemical Company.

All other brands are the property of their respective owners.

© Eastman Chemical Company, 2010.